

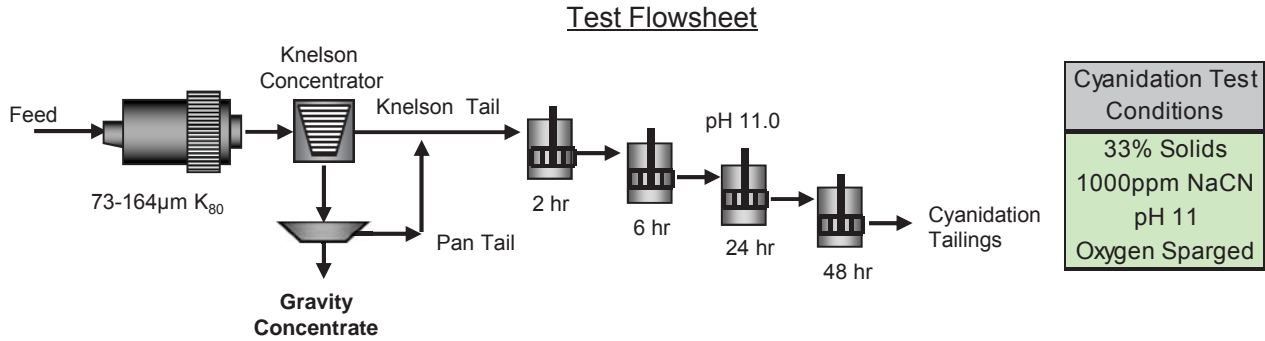


**FIGURE 1**  
**METALLURGICAL TEST RESULT SUMMARY**

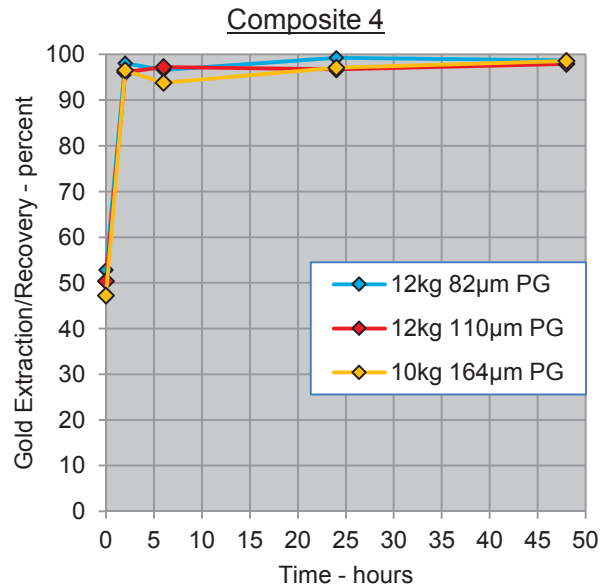

Average Cyanidation Leach Kinetics

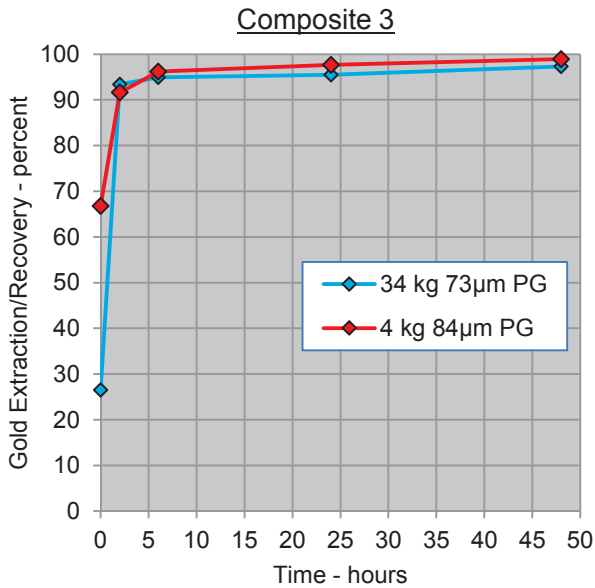

Note: Zero hour extraction indicates gravity recovery.

Overall Test Result Summary

Composite	Primary Grind µm K <sub>80</sub>	Feed Mass kg	Gravity Gold Recovery percent	Gravity Mass Recovery percent	Cyanidation Leach 48 Hour Gold Performance				Calculated Au Feed Grade - g/t	Overall Au Extraction/Gravity Recovery - percent
					Leach Test No.	Extraction percent	Reagent Cons. - g/tonne			
							NaCN	Lime		
Composite 3	73	33.8	29.7	0.03	5	95.5	0.06	0.27	0.90	96.8
					6	95.7	0.06	0.30		97.0
					7	97.2	0.07	0.28		98.0
					8	97.0	0.06	0.28		97.9
	84	3.9	67.1	0.15	16	96.6	0.01	0.28	0.93	98.9
					17	96.8	0.01	0.26	98.9	
Composite 4	82	11.8	54.2	0.06	9	96.1	0.07	0.30	1.22	98.2
					10	98.3	0.06	0.29	99.2	
	110	12	47.4	0.11	11	98.4	0.06	0.30	1.15	99.2
					12	93.2	0.06	0.28	96.4	
	164	9.8	50.4	0.11	13	98.1	0.04	0.28	1.08	99.0
					14	96.4	0.04	0.27	98.2	

Notes: a) Recalculated gold head grades from cyanidation leach tests were used to calculate Gravity Gold Recovery values.

b) Reagent Cons. – indicates reagent consumptions recorded in tests.

c) Complete test conditions and results can be located in Appendix II.